

# Mechanical Properties of Concrete after Addition of Different Types of Steel Fibres

Dr. K. Chandrasekhar Reddy<sup>1</sup>, S. Jagadeesh<sup>2</sup>

<sup>1</sup>Professor of Civil Engineering & Principal, Siddharth Institute of Engineering & Technology, Puttur, Andhra Pradesh, India.

<sup>2</sup>PG Student, Department of Civil Engineering, Siddharth Institute of Engineering & Technology, Puttur, Andhra Pradesh, India.

## ABSTRACT

*In this project effect of steel fibers on the strength of concrete for M 40 grade will be studied by varying the percentage of fibers in concrete and types of fibers. Compressive strength, Split Tensile Strength & Flexural strength will be compared and tabulated. Fibers addition to concrete results in more closely spaced and improved resistance to the cracks. Improvement observed in mechanical properties of controlled concrete due to present of steel fibers. There is a significant increase in Compressive Strength of concrete with addition of Crimped Steel Fiber when compared to Straight and Hooked Steel Fiber. The percentage increase in Compressive Strengths of Straight Steel Fiber (2%), Hooked Steel Fiber (2%) and Crimped Steel Fiber (2%) are 9.84%, 5.9% & 16.92% respectively. Similar trend is followed for other mechanical properties.*

**Keywords:** Crimped Steel Fiber, Straight Steel Fiber, Hooked Steel Fiber, Compressive strength, Split Tensile strength.

## 1. INTRODUCTION

Civil engineers and construction experts are aware of the fact that plain concrete exhibits very low tensile strength, limited ductility and little resistance to cracking, but are forced to use plain concrete due to the exigency. Hence there is an urgent need to reinforce the conventional concrete to cope up with tensile loads and strains suited to our needs. The presence of micro cracks at the mortar-aggregate interface is the inherent weakness of plain concrete. The application of load leads to propagation of cracks and brittle fractures in conventional concrete due to its poor tensile strength. Normally micro cracks appear in concrete during hardening stage. When load is applied, micro cracks start developing along the planes which may experience relatively low tensile strains at about 25-30% of the ultimate strength in compression. Further application of load leads to uncontrolled formation of the micro cracks. Concrete mix that contains short, discrete fibers that are uniformly distributed and randomly oriented is called Fiber reinforced concrete. The fibers used are steel fibers, synthetic fibers, glass fibers and natural fibers. The fibers in members resist the opening of the cracks due to micro cracking and increase the ability of the members to withstand loads.

## 2. LITERATURE REVIEW

**Kolhapure B.K. (2006)** was done on mechanical properties of concrete using recron 3S fibers along with super plasticizer. He concluded that compressive strength, tensile strength and flexural strength is increased by 30%, 23% and 24% respectively when compared to controlled concrete.

**Bischoff (2003)** The tension stiffening bond factor ( $\beta$ ) given by Bischoff (2003) is obtained by dividing the average load carried by the cracked concrete ( $P_{c,m}$ ) with the force carried by the concrete at first cracking ( $P_{cr}$ ), it can be used to predict tension stiffening of SFRC up to yielding of reinforcing steel.

**Kukreja and Chawla (1989)** after conducting experimental investigations on concrete by using straight bent and crimped steel fibers with aspect ratio 80, they published a paper on "flexural characteristics of steel fiber reinforced concrete". They reasoned that, in light of steel fiber content, its sort and introduction, conduct can extend from weak to extremely malleable, just for a similar scope of flexural quality.

**Ghosh et al.(1989)** in the wake of directing trials on cylinder split tensile strength and modulus of rupture of concrete by using low fiber content (0.4% to 0.7%) with straight steel fibers, they concluded that split cylinder testing method is recommended for determining the tensile strength of fiber - reinforced concrete as in the case of normal concrete.

**Swamy, R.N (1974)** after experimental investigations on the flexural strength of concrete by using small short steel fibers, he concluded that the first crack strength is significantly improved. Also he has derived equations to determine the first crack flexural and ultimate flexural strength of the composite based on experimental and previous investigations.

### 3. OBJECTIVE

The objective of this research was to investigate the following aspects of fiber reinforced beams made of medium-high concrete capacity. To assess the effectiveness of each type of fibers (hooked-end steel fibers, crimped-steel fibers and Straight-steel fibers) on Cube specimens & Cylinder Specimens. To determine the percentage of fibers to be added to improve Strength of concrete. This project deals with M40 Grade of Concrete

### 4. MATERIALS AND METHODS

#### 4.1 Properties of Materials

##### 4.1.1 Cement

In this study, Zuari Cement of 53 grade Ordinary Portland Cement conforming to IS: 12269–1987 was used for the entire work. The cement was purchased from single source and was used for casting of all specimens. The properties are shown in Table 1.

**Table 1:** Properties of cement

S. No	Characteristics	Test results	Requirements as per IS 12269 – 1987
1	Fineness (retained on 90- $\mu$ m sieve)	5%	<10%
2	Normal Consistency	33%	--
3	Initial setting time of cement	63 min's	30 minutes (minimum)
4	Final setting time of cement	450 min's	600 minutes (maximum)
5	Expansion in Le-chatelier's method	2 mm	10 mm (maximum)
6	Relative Density	3.15	3.10 – 3.25

##### 4.1.2 Fine Aggregate

Locally available natural (river) sand confirming to IS specifications was used as a fine aggregate in the concrete mix. The properties are shown in Table.2.

**Table 2:** Properties of Fine Aggregate

S. No	Test conducted	Results obtained	Permissible Limits as per IS 383 – 1970
1	Relative Density	2.67	2.5 to 3.0
2	Fineness modulus	2.77	--
4	Water absorption (%)	1.09	Max 3%
5	Sieve Analysis	Zone – II	--

##### 4.1.3 Coarse Aggregate

Locally available Crushed granite metal of nominal size 20 mm and 10 mm and confirming to IS specifications were used. The properties are shown in Table.3. The coarse aggregate was used for the concrete mix is a combination of 20 mm and 10 mm size aggregates in ratio 1.5: 1.0.

**Table 3:** Properties of Coarse Aggregate

S. No	Test conducted	Results obtained	Permissible Limits as per IS 383 – 1970
1	Relative Density	2.78	2.5 to 3.0
2	Fineness modulus	7.1	--

4	Water absorption (%)	1.20	Max 3%
5	Sieve Analysis	Zone – II	--

#### 4.1.4 Steel Fibres

**Table 4:** Properties of Steel fibers

S. No	Properties	Straight Fibre	Crimpt Fibre	Hooked Fibre
1	Length of Fibre	45 mm	36 mm	35 mm
2	Diameter of fibre	0.45 mm	0.45 mm	0.55 mm
3	Aspect ratio of Fibre	100	100	64
4	Ultimate Tensile strength of Fibre	500-600 N/mm <sup>2</sup>	600-700 N/mm <sup>2</sup>	1100 N/mm <sup>2</sup>
5	Density	7850 Kg/m <sup>3</sup>	7850 Kg/m <sup>3</sup>	7850 Kg/m <sup>3</sup>

#### 4.1.5 Water

Water used for casting and curing of concrete test specimens is free from impurities which when present can adversely influence the various properties of concrete.

#### 4.2 Concrete Mix Proportion

In the present experimental investigation, the influence of individual application of various types (straight, hooked and crimped) of steel fibers on M40 grade concrete is studied.

M40 grade of concrete were designed as per the Indian Standard code of practice. The various ingredients for one cubic meter of M40 grade concrete are shown in Table 5.

**Table 5:** Quantities of Ingredients per cum of M40 Grade Concrete

S. No	Mix Identification	Cement (kg's)	Fine Aggregate		Water (lit)	Steel Fibers (kg's)
			Sand (kg's)	Coarse Aggregate (kg's)		
1	C.C	360	704	1302	164	0
2	1% SF (Straight)	360	704	1302	164	78.50
3	2% SF (Straight)	360	704	1302	164	157
4	3% SF (Straight)	360	704	1302	164	235.5
5	1% SF (Hooked)	360	704	1302	164	78.50
6	2% SF (Hooked)	360	704	1302	164	157
7	3% SF (Hooked)	360	704	1302	164	235.5
8	1% SF (Crimped)	360	704	1302	164	78.50
9	2% SF (Crimped)	360	704	1302	164	157
10	3% SF (Crimped)	360	704	1302	164	235.5

#### 4.3 Test Specimens


Concrete test specimens consist of 150 mm × 150 mm × 150 mm cubes, cylinders of 150 mm diameter and 300 mm height and 100 mm × 100 mm × 500 mm prisms. Concrete cube specimens were tested at 3, 7 & 28 days of curing to obtain the compressive strength of concrete. Cylindrical and prism samples were tested at the age of 28 days curing to

obtain the split tensile strength and flexural strength of concrete respectively. The rate of loading is as per the Indian Standard code specifications.

**5. RESULTS AND DISCUSSIONS**


**5.1 Compressive Strength Results**

The variation of the cube compressive strength with the age of M40 grade concrete prepared using the various proportions of (1%, 2% & 3%) of Straight Steel Fibers, (1%, 2% & 3%) of Hooked Steel Fibers and (1%, 2% & 3%) of Crimped Steel Fibers is shown in Figure 1. Each value of the cube compressive strength indicates the average of three test results. It can be observed that all the Steel Fiber (Straight, Hooked & Crimped) Reinforced Concrete exhibits improved Compressive strength compared to Control Concrete up to 2% of Weight of Concrete. But, The compressive strength of concrete with 2% Crimped steel Fibers exhibits 16.92 % more Strength than the control concrete and other Fiber proportions.

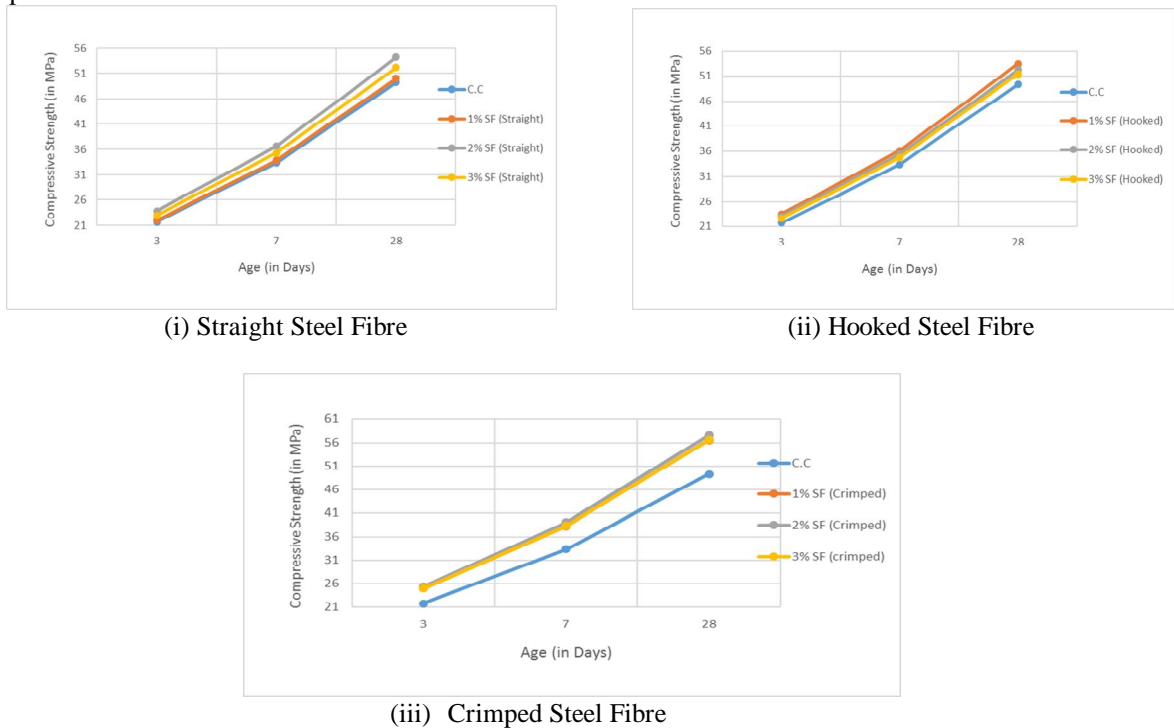

**Figure 1** Variation of the cube compressive strength with the age of M40 grade concrete prepared using the various proportions of (1%, 2% & 3%) of Straight Steel Fibers, (1%, 2% & 3%) of Hooked Steel Fibers and (1%, 2% & 3%) of Crimped Steel Fibers.


The variation of 7 days and 28 days cube compressive strength of M40 grades of concrete prepared with various proportions of (1%, 2% & 3%) of Straight Steel Fibers, (1%, 2% & 3%) of Hooked Steel Fibers and (1%, 2% & 3%) of Crimped Steel Fibers shown in Figure 2.

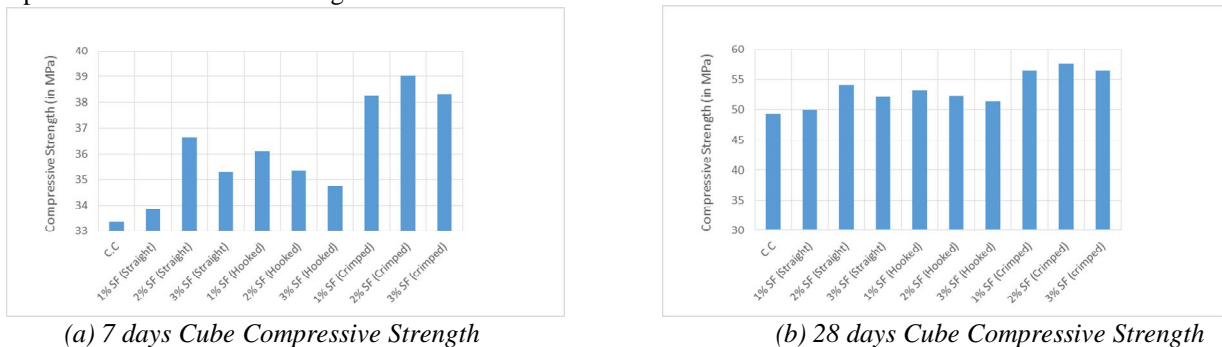

**Figure 2** Variation of 7 days and 28 days Cube Compressive Strength of M40 grades of concrete prepared with various proportions of (1%, 2% & 3%) of Straight Steel Fibers, (1%, 2% & 3%) of Hooked Steel Fibers and (1%, 2% & 3%) of Crimped Steel Fibers

**5.2 Split Tensile Strength Results**


The variation of split tensile strength of M40 grade of concrete Steel Fibers (Straight, Hooked & Crimped) is shown in Figure 3. The split tensile strength of M40 grade of control concrete is 4.59 MPa. The split tensile strength of Steel Fiber (Straight, Hooked & Crimped) Reinforced Concrete exhibits improved strength compared to Control Concrete up to 2% of Volume of Concrete, The Concrete with 2% of Crimped Steel Fiber possesses higher Split Tensile Strength when compared to all other proportions and with further increase in the content of Steel Fiber.

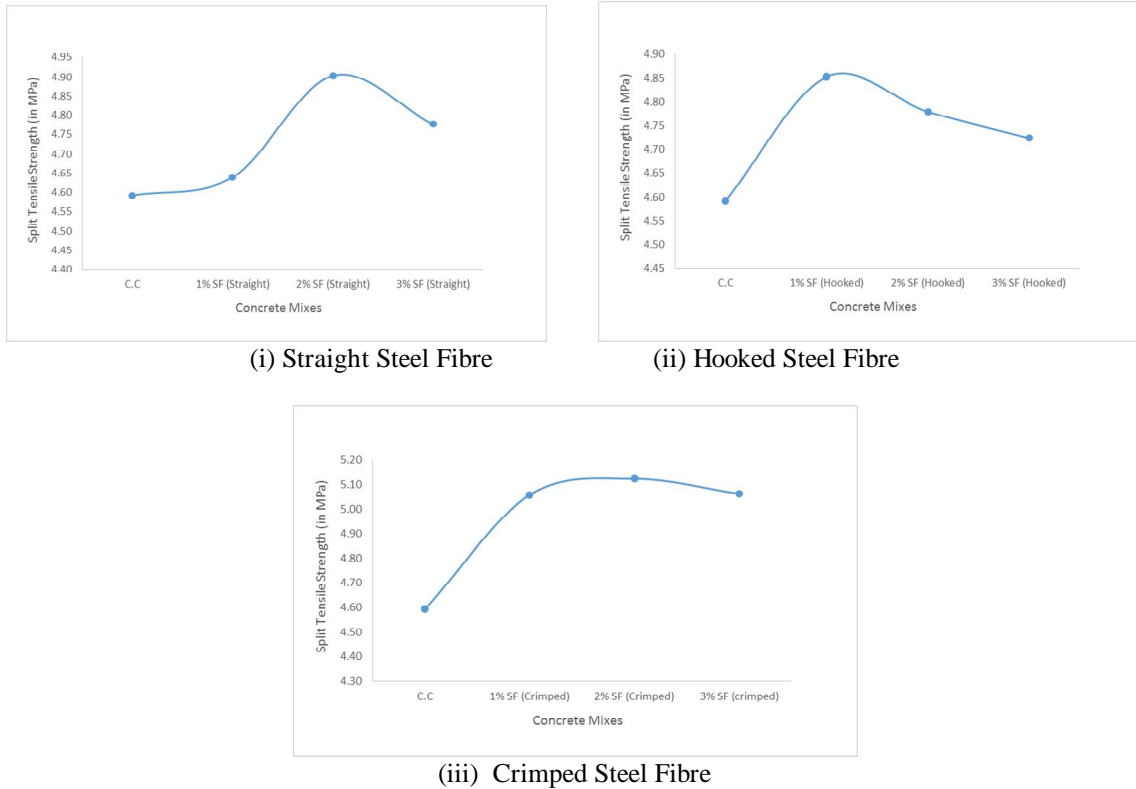


**Figure 3** Variation of Split Tensile Strength of M40 grade of concrete Steel Fibers (Straight, Hooked and Crimped).

**5.3 Flexural Strength Results**

The variation of Flexural strength of M40 grade of concrete Steel Fibers (Straight, Hooked and Crimped) is shown in Figure 4. The Flexural strength of M40 grade of control concrete is 7.12 MPa. The Flexural strength of all the Steel Fiber (Straight, Hooked & Crimped) Reinforced Concrete exhibits improved strength compared to Control Concrete up to 2% of Weight of Concrete, The Concrete with 2% of Crimped Steel Fiber possesses higher Flexural Strength when compared to all other proportions and with further increase in the content of Steel Fiber.

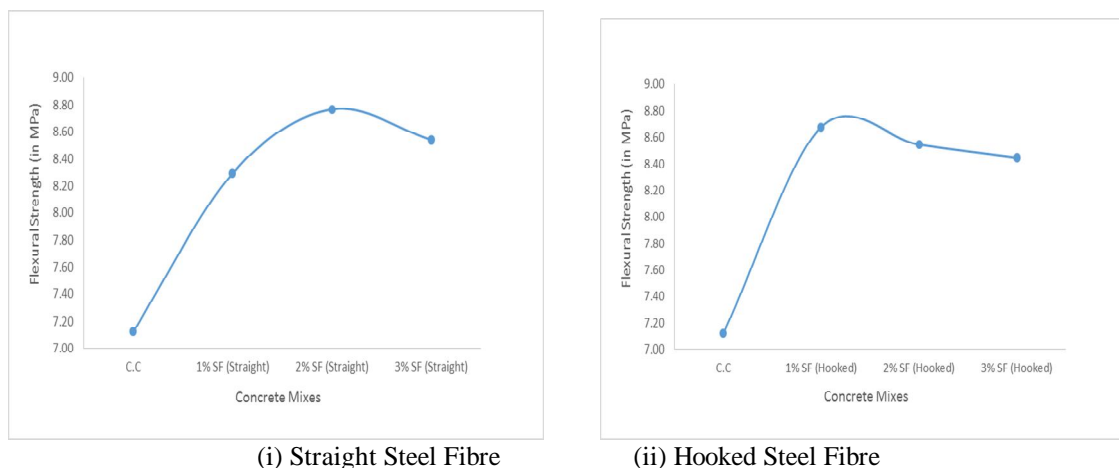

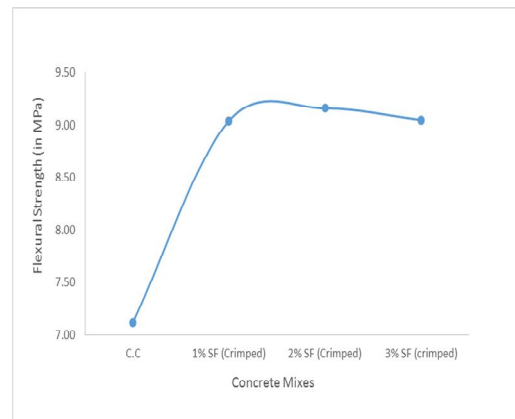

(iii) Crimped Steel Fibre

**Figure 4** Variation of Flexural Strength of M40 grade of concrete Steel Fibers (Straight, Hooked and Crimped).

## 6. CONCLUSIONS

Plain cement concrete is a brittle material and fails suddenly. Addition of steel fibers to concrete changes its brittle mode of failure into a more ductile one and improves the post cracking behavior of concrete. Fibers addition to concrete results in more closely spaced reducing the crack width and improved resistance to the cracks. There is a significant increase in Compressive Strength of concrete with addition of Crimped Steel Fiber when compared to Straight and Hooked Steel Fiber. The percentage increase in Compressive Strengths of Straight Steel Fiber (2%), Hooked Steel Fiber (2%) and Crimped Steel Fiber (2%) are 9.84%, 5.9% & 16.92% respectively. The percentage increase in Split Tensile Strengths of Straight Steel Fiber (2%), Hooked Steel Fiber (2%) and Crimped Steel Fiber (2%) are 6.75%, 4.13% and 11.5% respectively. Ductility is increased due to the addition of crimped steel fibers to OPC. The presence of steel fibers with higher content reduced the crack propagation in OPC. The percentage increase in Flexural Strength of Straight Steel Fiber (2%), Hooked Steel Fiber (2%) and Crimped Steel Fiber (2%) are 23.17%, 19.95% and 28.66% respectively.

## REFERENCES

- [1]. ACI committee, "Measurement of properties of fibre reinforced concrete", ACI Materials Journal, Nov-Dec 1988.
- [2]. Bischoff, Peter H "Tension stiffening and cracking of steel fibre reinforced concrete", Journal of Materials in Civil Engineering. ASCE, March / April, 2003.
- [3]. Ghosh, S., Bhattacharya, C., and Ray, S.P. (1989)., "Split tensile strength of steel fiber reinforced concrete", Journal of the Institution of Engineers (India), Vol.69, January 1989, pp. 222-227.
- [4]. Kolhapure. B.K., "Study Mechanical properties of Recron 3S fiber reinforced concrete with super plasticizer", Proceedings of the National Conference on Concrete Technology for the Future at Kongu Engineering College, Erode, 2006, pp-449-455.
- [5]. Kukreja, C.B. and Chawla, Sanjeev., "Flexural properties of steel fiber reinforced concrete", Indian Concrete Journal, March 1989, pp. 246-252.
- [6]. Nagarkar, P.K., Tambe, S.K. and Pazare, D.G., "study of fibre reinforced concrete", Proceedings of the International symposium on fibre reinforced concrete, Dec. 16-19, 1987, Madras, India, pp.2.131-2.141.
- [7]. Ramakrishnan.V, G.Y.Wu, and G.Hosalli, "Flexural behavior and toughness of fibre reinforced concrete", Transportation Research Record, No.1226, 1989a, pp.69 – 77.
- [8]. Romualdi, J.P. & Batson, G.B. 1963. Mechanics of crack arrest in concrete, Journal of Engineering Mechanics 89: 147-168.
- [9]. Swamy, R.N., "Mechanical properties, and applications of Fiber reinforced concrete", Indian Concrete Journal, January 1974, pp. 7-16.

## AUTHORS



**Dr. K. Chandrasekhar Reddy** received B.Tech from SVU, M.Tech from NIE and Ph.D from SVU. He is having more than two decades of experience in teaching and industry. He has wide experience as a Civil Engineer, Teacher and as an Administrator. He has published more than fifty papers.



**S. Jagadeesh** is pursuing Master of Technology in Structural Engineering in Siddharth Institute of Engineering & Technology, Puttur, AP, India.